

Effect of Milling Process Parameters on the Surface Roughness of CFRP

Prof. P. R. Parekh

Research Scholar, Gujarat Technological University

Prof. P. D. Patel

Assistant Professor, Dept.of Automobile L. D. College of Engineering, Ahmedabad

Prof. B. C. Khatri

Associate Professor, Dept.of Mechanical, Government Engineering College, Modasa

Prof. U. V. Shah

Professor, Dept. of Mechanical, Government Engineering College, Modasa

Abstract

Carbon fiber reinforced plastic composites possess excellent mechanical properties, and therefore these materials are widely used industries like the automobile, defense, aerospace sectors. However the machining of CFRP materials is difficult, but the mechanical machining of these material is prime requirement to meet dimensional accuracy. With showing this problem, the main objective of the present paper is to special solid carbide end mill that are used for milling carbon fiber reinforced polymer composites during trimming, slotting operation. Depth of cut and feed rate are primary cutting parameters that affect the surface roughness. An increase in the depth of cut and feed rate tends to produce a rougher surface due to the increased material removal rate. On the other hand, increasing the spindle speed can decrease surface roughness by reducing the tool's contact time with the work piece. Tool coatings such as DLC (Diamond-Like Carbon) and ALCRN (Aluminum Chromium Nitride) can also affect surface roughness. These coatings have a lower coefficient of friction than uncoated tools, resulting in less heat generation during machining. This reduced heat generation can result in a smoother surface finish. In summary, selecting appropriate cutting parameters and tool coatings can help in achieving the desired surface roughness for a given machining operation.

Keywords: Machining, milling, CFRP, surface roughness, Coating

I. Introduction

Fiber reinforced plastics are among the most high-performance materials in the field of light-weight design due to their exceptional weight-specific qualities. They are especially intriguing for structural components in the aerospace and space industries due of their high specific strength and stiffness. [1]. Additionally, the use of fibre reinforced plastics is rising in the fields of automotive, medical, and general engineering since they open up new possibilities for product development and design. [2,3]. Although carbon fibre reinforced plastic (CFRP) components are typically produced close to net shape, they must be machined to create bore holes or notches in the workpiece and to enhance the quality of contact or functional surfaces. [4]. The process of machining is frequently carried out by milling, drilling, or grinding When compared to metallic alloys, CFRP's machining characteristics are fundamentally different, and the cutting mechanism is still mostly understood. [3,5,6,7,8]. The mechanical properties of the CFRP, which are influenced by

the kind of fibre, the matrix material, the volume of the fibres, the orientation of the fibres, and the manufacturing method, have a significant impact on the machinability. It is challenging to identify relationships with broad applicability due to the abundance of affecting elements. Because CFRP is an inhomogeneous and anisotropic material, processing it can be challenging due to issues including fibre pull-out, delamination, and matrix material breakdown, which deteriorates the surface quality and material attributes. Thermal impacts have a significant impact on the mechanical characteristics of matrix materials in particular. [9]. In contrast, carbon fibres can withstand temperatures of up to 3000°C before the structure starts to degrade. In the present study an up-cut milling process of unidirectional CFRP is investigated. Finding a link between the cutting conditions and parameters and the surface integrity of the milled workpiece is the goal of this study. As a result, the workpiece temperature, cutting speed, and fibre orientation have all been adjusted. Cross-sectional micrographs of the specimen are analysed to find probable damages at the machined surface.

II Experimental procedure



Figure 1. Surface Roughness Model

All cutting experiments have been carried out on a three-axis CNC machine BFW make BMV 40 model using a solid carbide rougher endmill with 18mm cutting diameter. Here using 03 type of solid carbide endmill with same geometry, six flute but varies with DLC coating,

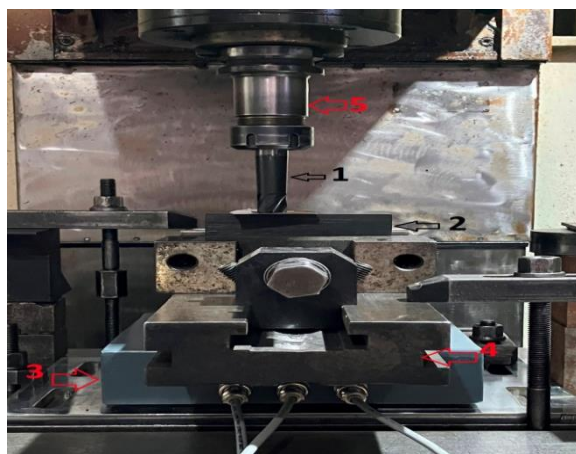


Figure 2. Experimental setup used for milling CFRP

ALCRN coating and Un-coated. Helix angle is 30 degree for all solid carbide endmill and shank diameter is 20mm. An milling process was applied under dry conditions to machine a slot into the CFRP specimens. Size of specimen is 125 x 125 x 30 mm. Within the investigations the spindle speed(rpm), feed rate (mm/min) and depth of cut(mm) were varied according to table 1. CFRP specimen clamped on Precision modular vice and Endmill cutter clamped in BT40 Collet Chuck Holder The test setup is shown in figure 2. The Surface Roughness measurement by Mahr make Marsurf PS 10 model (Fig.1)

(1) Solid Carbide End mill , (2) CFRP Material, (3) Milling Tool Dynamometer , (4) Precision Modular Vice, (5) BT40 Collet Chuck Holder



Figure 3. Coating end mill

Table 1. Using DLC Coated End mill

SPEED (rpm)	FEED RATE (mm/min)	Depth of Cut (mm)	Surface Roughness (u_m)
1500	250	0.2	0.862
1500	250	0.35	1.993
1500	250	0.5	0.846
2575	350	0.2	1.012
2575	350	0.35	1.965
2575	350	0.5	1.682
4000	450	0.2	1.466
4000	450	0.35	2.626
4000	450	0.5	2.993

Table 2. Using ALCRN Coated End mill

SPEED (rpm)	FEED RATE (mm/min)	Depth of Cut (mm)	Surface Roughness (u_m)
1500	250	0.2	1.105
1500	250	0.35	1.276
1500	250	0.5	0.888
2575	350	0.2	0.993
2575	350	0.35	0.987
2575	350	0.5	1.759
4000	450	0.2	1.033
4000	450	0.35	0.98
4000	450	0.5	0.938


Table 3. Using Un Coated End mill

SPEED (rpm)	FEED RATE (mm/min)	Depth of Cut (mm)	Surface Roughness (u_m)
1500	250	0.2	0.975
1500	250	0.35	0.951
1500	250	0.5	0.983
2575	350	0.2	0.92
2575	350	0.35	0.864
2575	350	0.5	1.111
4000	450	0.2	1.182
4000	450	0.35	1.964
4000	450	0.5	2.003

III Results and discussion

- 1) Influence of milling parameter on the surface roughness(u_m) by using DLC coated end mill

Based on the given data, we can observe the following trends Surface roughness varies significantly with different combinations of speed, feed rate, and depth of cut. In some cases, increasing the depth of cut results in an increase in surface roughness, while in other

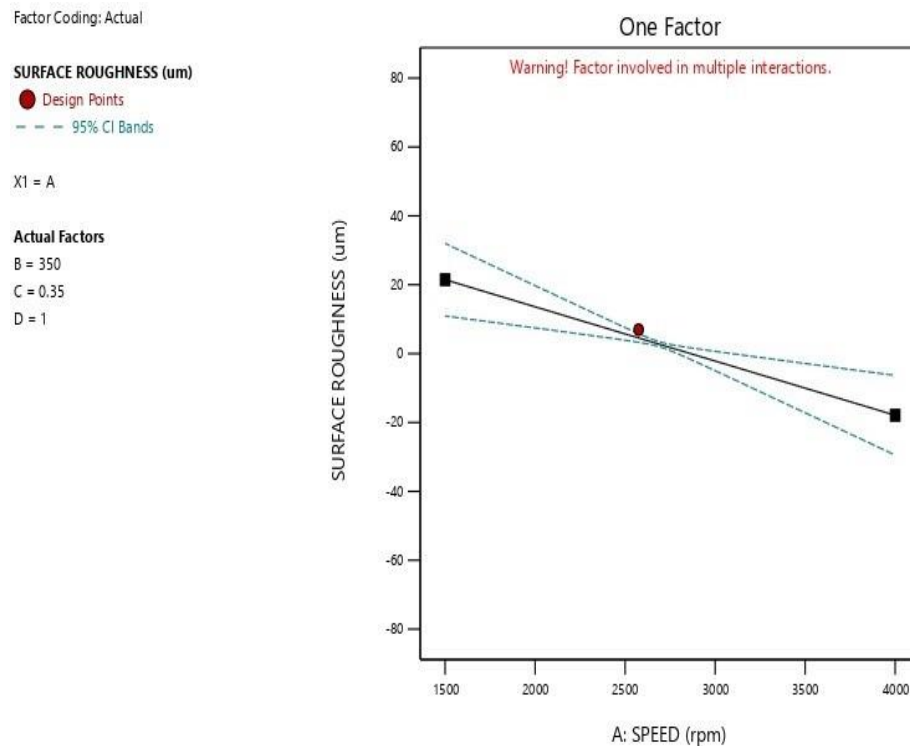

cases it results in a decrease.

Figure 4. DLC Coating end mill

In general, higher speeds and feed rates tend to produce higher surface roughness, although this is not always the case. To determine the optimal cutting conditions for minimizing surface roughness, we can look for combinations of speed and feed rate that produce the lowest surface roughness values for a given depth of cut. For a depth of cut of 0.2 mm, the optimal cutting conditions are at a speed of 1500 rpm and a feed rate of 250 mm/min, which produce a surface roughness of 0.862 um. For a depth of cut of 0.35 mm, the optimal cutting conditions are at a speed of 2575 rpm and a feed rate of 350 mm/min, which produce a surface roughness of 1.965um. For a depth of cut of 0.5 mm, the optimal cutting conditions are at a speed of 1500 rpm and a feed rate of 250 mm/min, which produce a surface roughness of 0.846 um. Note that these optimal conditions are based solely on minimizing surface roughness and do not take into account other factors such as tool wear, tool life, or machining time. Additionally, the optimal conditions may differ for different types of materials being machined.

2) Influence of milling parameter on the surface roughness (u_m) by using ALCRN coated end mill

To determine the optimal cutting conditions for minimizing surface roughness, we can look for combinations of speed and feed rate that produce the lowest surface roughness values for a given depth of cut. For a depth of cut of 0.2 mm, the optimal cutting conditions are at a speed of 2575 rpm and a feed rate of 350 mm/min, which produce a surface roughness of

0.993 μm . For a depth of cut of 0.35 mm, the optimal cutting conditions are at a speed of 4000 rpm and a feed rate of 450 mm/min, which produce a surface roughness of 0.98 μm . For a depth of cut of 0.5 mm, the optimal cutting conditions are at a speed of 1500 rpm and a feed rate of 250 mm/min, which produce a surface roughness of 0.888 μm .

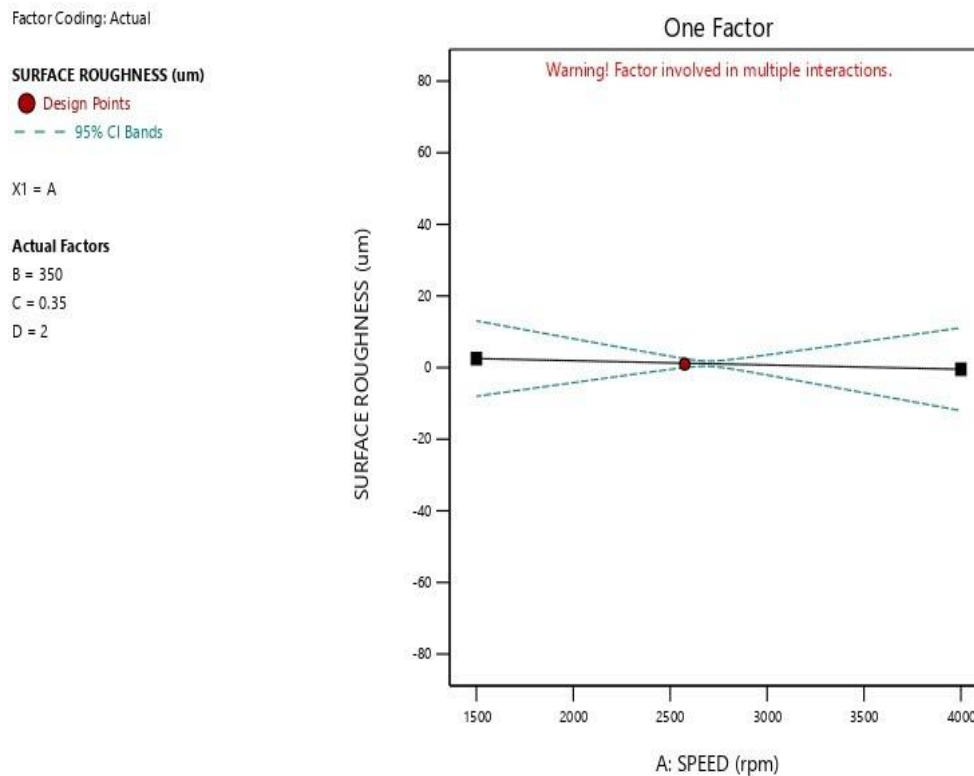


Figure 5. ALCRN Coating end mill

3) Influence of milling parameter on the surface roughness (μm) by using Un coated end mill

For a depth of cut of 0.2 mm, the optimal cutting conditions are at a speed of 2575 rpm and a feed rate of 350 mm/min, which produce a surface roughness of 0.92 μm . For a depth of cut of 0.35 mm, the optimal cutting conditions are at a speed of 1500 rpm and a feed rate of 250 mm/min, which produce a surface roughness of 0.864 μm . For a depth of cut of 0.5 mm, the optimal cutting conditions are at a speed of 1500 rpm and a feed rate of 250 mm/min, which produce a surface roughness of 0.983 μm .

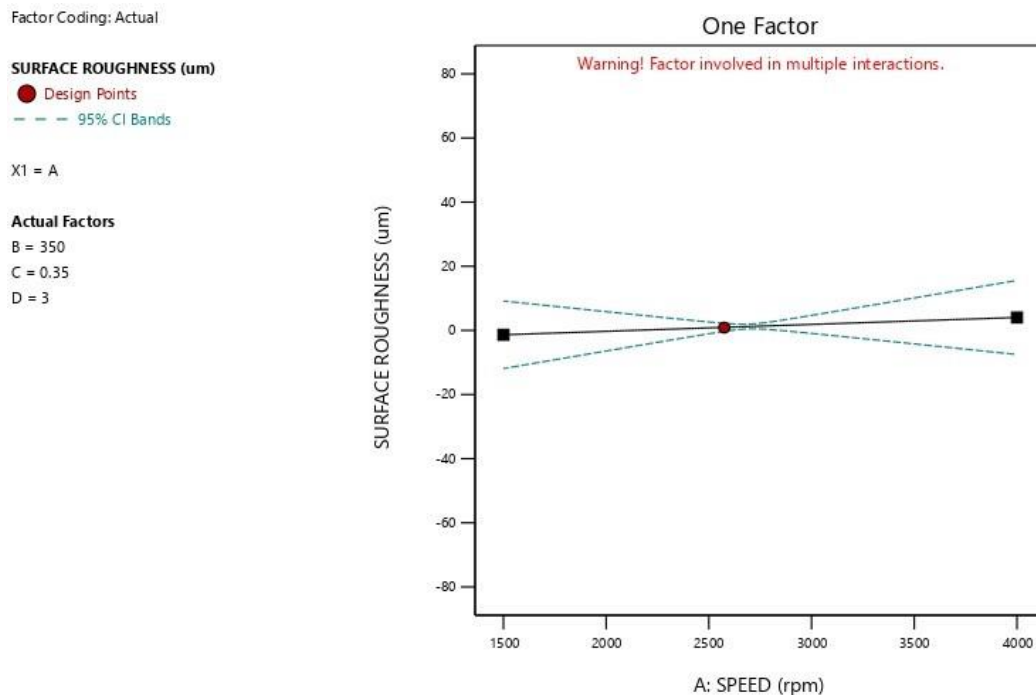


Figure 6. Uncoating end mill

IV Conclusion

The table provided shows the surface roughness produced by different cutting conditions and tool coatings. The cutting conditions are represented by the spindle speed (rpm), feed rate (mm/min), and depth of cut (mm). The tool coatings used are DLC coating, ALCRN coating, and uncoated.

It can be observed that the surface roughness is affected by the cutting conditions and the tool coating. In general, increasing the depth of cut and the feed rate tends to increase the surface roughness, while increasing the spindle speed tends to decrease it. Additionally, the DLC coating and the ALCRN coating generally produce smoother surfaces than the uncoated tool.

For example, at a spindle speed of 1500 rpm, a feed rate of 250 mm/min, and a depth of cut of 0.2 mm, the DLC coating produces a surface roughness of 0.862 um, while the ALCRN coating produces a surface roughness of 1.105 um, and the uncoated tool produces a surface roughness of 0.975 um. At a higher spindle speed of 4000 rpm, a higher feed rate of 450 mm/min, and a higher depth of cut of 0.5 mm, the DLC coating produces a surface roughness of 2.993 um, while the ALCRN coating produces a surface roughness of 0.938 um, and the uncoated tool produces a surface roughness of 2.003 um.

References

- [1] Brinksmeier, E., Fangmann, S. and Rentsch, R., 2011. Drilling of composites and resulting surface integrity. *CIRP annals*, 60(1), pp.57-60.
- [2] Chang, C.S., 2006. Turning of glass-fiber reinforced plastics materials with chamfered main cutting edge carbide tools. *Journal of materials processing technology*, 180(1-3), pp.117-129.
- [3] Teti, R., 2002. Machining of composite materials. *CIRP Annals*, 51(2), pp.611-634.

- [4] Schulze, V., Becke, C. and Pabst, R., 2011. Specific machining forces and resultant force vectors for machining of reinforced plastics. *CIRP annals*, 60(1), pp.69-72.
- [5] Davim, J.P. and Reis, P., 2005. Damage and dimensional precision on milling carbon fiber-reinforced plastics using design experiments. *Journal of materials processing technology*, 160(2), pp.160-167 [6] Ferreira, J.R., Coppini, N.L. and Miranda, G.W.A., 1999. Machining optimisation in carbon fibre reinforced composite materials. *Journal of materials processing technology*, 92, pp.135-140.
- [7] Hu, N.S. and Zhang, L.C., 2004. Some observations in grinding unidirectional carbon fibre-reinforced plastics. *Journal of materials processing technology*, 152(3), pp.333-338.
- [8] Bhatnagar, N.B.A.I.I.O.T., Ramakrishnan, N., Naik, N.K. and Komanduri, R.B.A.O.S.U., 1995. On the machining of fiber reinforced plastic (FRP) composite laminates. *International journal of machine tools and manufacture*, 35(5), pp.701-716.
- [9] Zheng, X., 2006. Nonlinear strain rate dependent composite model for explicit finite element analysis (Doctoral dissertation, University of Akron).
- [10] Davim, J.P. and Reis, P., 2005. Damage and dimensional precision on milling carbon fiber-reinforced plastics using design experiments. *Journal of materials processing technology*, 160(2), pp.160-167.
- [11] Madhu, S. and Balasubramanian, M., 2017. Effect of abrasive jet process parameters on machining glass fibre reinforced polymer composite: Einfluss der abrasiven Strahl-Prozessparameter zur Bearbeitung glasfaserverstärkter Polymer-Verbundwerkstoffe. *Materialwissenschaft und Werkstofftechnik*, 48(11), pp.1146-1157.
- [12] Ema, S. and Davies, R., 1989. Cutting performance of end mills with different helix angles. *International Journal of Machine Tools and Manufacture*, 29(2), pp.217-227.
- [13] Ghafarzadeh, S., Lebrun, G. and Chatelain, J.F., 2016. Experimental investigation of the cutting temperature and surface quality during milling of unidirectional carbon fiber reinforced plastic. *Journal of Composite Materials*, 50(8), pp.1059-1071.
- [14] Gordon, S. and Hillery, M.T., 2003. A review of the cutting of composite materials. *Proceedings of the Institution of Mechanical Engineers, Part L: Journal of Materials: Design and Applications*, 217(1), pp.35-45.
- [15] Waqar, S., He, Y., Abbas, C.A. and Majeed, A., 2017, August. Optimization of cutting tool geometric parameters in milling of CFRP laminates. In *21st International Conference on Composite Materials (Vol. 25)*.
- [16] Fan, W. ed., 2012. *Key Engineering Materials II*. Trans Tech Publications.
- [17] MATERIALA, R.K.P., 2016. Investigation of the cutting forces and surface roughness in milling carbon-fiber-reinforced polymer composite material. *Materiali in tehnologije*, 50(4), pp.591-600. [18] López, N., De Lacalle, A., Lamikiz, F.J., Campa, A.F. and Valdivielso, E.I., 2010. Milling of carbon fiber reinforced plastics López. *J Compos Mater*, 83, pp.49-55.
- [19] Ghafarzadeh, S.B., Chatelain, J.F. and Lebrun, G., 2013. Multi axis machining of high performance CFRP for aerospace industry. In *19th International Conference on Composite Materials (ICCM19)*.
- [20] Hashish, M. and Kent, W.A., 2013, September. Trimming of CFRP aircraft components. In *WJTA-IMCA conference and Expo*.
- [21] Guerra, A., Roca, A. and de Ciurana, J., 2017. A novel 3D additive manufacturing machine to biodegradable stents. *Procedia Manufacturing*, 13, pp.718-723.
- [22] Chibane, H., Serra, R. and Leroy, R., 2017. Optimal milling conditions of aeronautical composite material under temperature, forces and vibration parameters. *Journal of Composite Materials*, 51(24), pp.3453-3463.
- [23] An, Q., Ming, W., Cai, X. and Chen, M., 2015. Effects of tool parameters on cutting force in orthogonal machining of T700/LT03A unidirectional carbon fiber reinforced polymer laminates. *Journal of Reinforced Plastics and Composites*, 34(7), pp.591-602.
- [24] Azmi, A.I., 2013. Chip formation studies in machining fibre reinforced polymer composites.

- International Journal of Materials and Product Technology, 46(1), pp.32-46.
- [25] Chatelain, J.F. and Zaghbani, I., 2012. Effect of tool geometry special features on cutting forces of multilayered CFRP laminates. *Journal of Composite Materials*, 85, p.90.
- [26] Sorrentino, L. and Turchetta, S., 2014. Cutting forces in milling of carbon fibre reinforced plastics. *International Journal of Manufacturing Engineering*, 2014.
- [27] Haddad, M., Zitoune, R., Eyma, F. and Castanie, B., 2014. Study of the surface defects and dust generated during trimming of CFRP: Influence of tool geometry, machining parameters and cutting speed range. *Composites Part A: Applied Science and Manufacturing*, 66, pp.142-154.
- [28] Chen, T., Wang, D., Gao, F., Liu, X. (2017). Ex- perimental study on milling CFRP with staggered PCD cutter. *Applied Sciences (Switzerland)*, 7(9). <https://doi.org/10.3390/app7090934>
- [29] Çelik, Y.H., Kilickap, E. and Kilickap, A.İ., 2019. An experimental study on milling of natural fiber (jute)-reinforced polymer composites. *Journal of Composite Materials*, 53(22), pp.3127-3137.
- [30] Çelik, Y.H., Kılıçkap, E. and Yardımeden, A., 2013. Investigation of experimental study of end milling of CFRP composite.
- [31] Nguyen-Dinh, N., Bouvet, C. and Zitoune, R., 2020. Influence of machining damage generated during trimming of CFRP composite on the compressive strength. *Journal of Composite Materials*, 54(11), pp.1413-1430.
- [32] Slamani, M., Chatelain, J.F. and Hamedanianpour, H., 2019. Influence of machining parameters on surface quality during high speed edge trimming of carbon fiber reinforced polymers. *International Journal of Material Forming*, 12, pp.331-353.